








RESEARCH ARTICLE | JULY 28 2025

Strain dependence of the Bloch domain component in 180° domains in bulk PbTiO_3 from first-principles

Special Collection: **Ferroic Materials, Domains, and Domain Walls: Bridging Fundamentals with Next-Generation**

Technology

Stephen Chege ; Louis Bastogne ; Fernando Gómez-Ortiz ; James Sifuna ; George Amolo ; Philippe Ghosez ; Javier Junquera *J. Appl. Phys.* 138, 044105 (2025)<https://doi.org/10.1063/5.0279988>

Articles You May Be Interested In

Low temperature magnetism in the perovskite substrate DyScO_3 *Appl. Phys. Lett.* (April 2009)Fine tuning epitaxial strain in ferroelectrics: $\text{Pb}_x\text{Sr}_{1-x}\text{TiO}_3$ on DyScO_3 *Appl. Phys. Lett.* (December 2010)Tunable electronic transport properties of DyScO_3 / SrTiO_3 polar heterointerface*Appl. Phys. Lett.* (March 2011)

Nanotechnology & Materials Science



Optics & Photonics



Impedance Analysis



Scanning Probe Microscopy



Sensors



Failure Analysis & Semiconductors



Unlock the Full Spectrum.

From DC to 8.5 GHz.

Your Application. Measured.

[Find out more](#)

Strain dependence of the Bloch domain component in 180° domains in bulk PbTiO_3 from first-principles

Cite as: J. Appl. Phys. 138, 044105 (2025); doi: 10.1063/5.0279988

Submitted: 9 May 2025 · Accepted: 8 July 2025 ·

Published Online: 28 July 2025



Stephen Chege,^{1,a)} Louis Bastogne,² Fernando Gómez-Ortiz,² James Sifuna,^{1,3} George Amolo,¹ Philippe Ghosez,² and Javier Junquera^{4,b)}

AFFILIATIONS

¹Materials Modeling Group, Department of Physics, Earth and Environmental Sciences, The Technical University of Kenya, 52428-00200 Nairobi, Kenya

²Theoretical Materials Physics, Q-MAT, Université de Liège, Allée du 6 août, 19, B-4000 Sart-Tilman, Belgium

³Theoretical Condensed Matter Group, Department of Natural Science, The Catholic University of Eastern Africa, 62157-00200 Nairobi, Kenya

⁴Departamento de Ciencias de la Tierra y Física de la Materia Condensada, Universidad de Cantabria, Avenida de los Castros s/n, 39005 Santander, Spain

Note: This paper is part of the Special Topic, Ferroic Materials, Domains, and Domain Walls: Bridging Fundamentals with Next-Generation Technology.

^{a)}schege882@gmail.com

^{b)}Author to whom correspondence should be addressed: javier.junquera@unican.es

ABSTRACT

We investigate the emergence of Bloch-type polarization components in 180° ferroelectric domain walls in bulk PbTiO_3 under varying mechanical boundary conditions, using first-principles simulations based on density functional theory. A spontaneous Bloch component—primarily associated with Pb displacements confined within the PbO domain wall plane—can condense under realistic strain conditions on top of the Ising-type domain walls. The amplitude and energetic stabilization of this component are highly sensitive to the in-plane lattice parameters. In particular, tensile strains akin to those imposed by DyScO_3 substrates enhance the Bloch component and lead to energy reductions as large as 10.7 mJ/m^2 ($10.6 \text{ meV}/\square$, where \square stands for “per domain wall unit cell”) with respect to the most stable structure including only Ising and Néel components. We identify a relatively flat energy landscape for the Bloch polarization, highlighting the tunability of chiral textures through strain engineering. Our results offer a predictive framework for estimating the strain-dependent onset temperature of Bloch-type domain wall components and provide insight into the design of topologically nontrivial and chiral polar structures in ferroelectrics.

© 2025 Author(s). All article content, except where otherwise noted, is licensed under a Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>). <https://doi.org/10.1063/5.0279988>

I. INTRODUCTION

For a long time, it was widely believed that ferroelectrics could not sustain intricate topological arrangements of electric dipoles. The strong coupling between polarization and the lattice was thought to impose significant structural and dipolar anisotropy, making polarization rotation prohibitively expensive in terms of energy.

However, pioneering theoretical studies on nanodots and nanodisks in the early 2000s,^{1,2} followed by combined theoretical and experimental investigations, have challenged this view. These efforts uncovered a variety of nontrivial topological structures—such as flux-closure patterns,^{3,4} vortices,⁵ electric skyrmion bubbles,^{6–8} merons,^{9–11} and hopfions,¹² among others—laying the foundation for an emerging field.

In low-dimensional ferroelectric oxide nanostructures, the interplay between electrostatic energies (arising from confinement and depolarization effects), elastic contributions, and gradient terms can significantly influence polarization patterns, leading to the stabilization of topologically nontrivial polar structures. For a more comprehensive overview of this rapidly evolving research area, readers may refer to Refs. 13–15.

One of the most extensively studied systems in this context is the $\text{PbTiO}_3/\text{SrTiO}_3$ heterostructure. As a consequence of the complex polar orderings, exotic functional properties may emerge as it is the case of the negative capacitance effect.^{16–18} Another interesting example is related to the appearance of chirality,^{19–22} even though both constituent materials are achiral in their bulk forms. The intricate relationship between chirality and topology in ferroelectric nanostructures has been extensively reviewed in Refs. 23 and 24.

Chirality, which describes a structural asymmetry where an object cannot be superimposed onto its mirror image, is a fundamental property with profound implications across multiple disciplines, including chemistry, physics, mathematics, and biology.^{25,26} In either magnetically or electrically polar systems, the presence of a vortex with a nonzero toroidal moment does not necessarily imply chirality in three dimensions. Depending on the symmetry of the mirror plane, a vortex structure may either be superimposable onto its mirror image or require only a rigid translation of half a unit cell. As a result, such vortices exhibit chirality primarily in two-dimensional systems, where symmetry transformations are constrained to those preserving dipole orientations within the plane.

In magnetism, long-range chiral ordering typically originates from the Dzyaloshinskii–Moriya interaction (DMI).^{27,28} Only recently have electric analogs of this interaction been proposed,^{29–31} where oxygen octahedral tilting mediates the coupling of an electric DMI, playing a role analogous to spin–orbit coupling in magnetic systems. However, this mechanism is absent in both bulk PbTiO_3 and $\text{PbTiO}_3/\text{SrTiO}_3$ heterostructures.

Crucially, ferroelectric systems do not require DMI-like interactions to exhibit chirality. For example, chiral behavior in electric polar vortices can arise from the coupling between an axial polarization component (perpendicular to the vortex plane) and the vorticity of clockwise or counterclockwise vortices. This phenomenon was first predicted in $\text{BaTiO}_3/\text{SrTiO}_3$ nanocomposites using first-principles-based effective Hamiltonians.³² The emergence of this axial polarization component is linked to the condensation of Bloch domain walls in ferroelectric domains.³³ Specifically, a 180° ferroelectric domain wall develops a Bloch component when the polarization rotates within a plane-parallel to the domain wall.³⁴ Given its fundamental implications, several studies have explored the formation and stability of Bloch-type domain walls.

Surprisingly, early first-principles calculations on 180° domain walls in bulk PbTiO_3 did not detect the presence of a Bloch polarization component.³⁵ The reasons remain unclear but may stem from symmetry constraints imposed during structural relaxations to reduce computational cost or from the choice of initial geometry, which could trap the system in a local energy maximum. The first *ab initio* evidence of a switchable Bloch component in PbTiO_3

domain walls was reported by Wojdel and Íñiguez,³³ using the first-principles calculations at $T = 0$ K with a PBEsol-based functional.³⁶ They observed a Bloch polarization component of approximately 0.4 C/m^2 at the domain wall plane, which rapidly vanished within the adjacent domains. Its origin was attributed to the large Pb atomic displacements and Pb–O hybridization at the domain wall.^{33,37,38}

The development of Bloch-like domain walls plays a crucial role in the condensation of polar Bloch skyrmions in single-phase PbTiO_3 .⁷ It is also linked to the emergence of vortex tubes in $\text{SrTiO}_3/\text{PbTiO}_3$ heterostructures grown on DyScO_3 substrates, endowing them with a distinct handedness.¹⁹ Notably, these chiral properties can be externally controlled via an applied electric field.³⁹ The condensation of the Bloch component in $\text{PbTiO}_3/\text{SrTiO}_3$ heterostructures at sufficiently low temperatures has been confirmed using first-principles,⁴⁰ second-principles,¹⁹ deep potential molecular dynamics,⁴¹ and phase-field perturbation models.⁴²

However, recent studies suggest that the predicted Bloch polarization component in 180° domain walls within $\text{PbTiO}_3/\text{SrTiO}_3$ heterostructures may be more sensitive to boundary conditions than previously thought.⁴³ Key factors such as epitaxial strain from the substrate, layer thickness, temperature, and equilibrium domain periodicity significantly influence its stabilization and can even suppress its formation. This complexity is further highlighted by the observation of Néel-type domain structures in PbTiO_3 thin films at room temperature, where a clear Bloch component is absent, suggesting at best a metastable nature.⁴⁴

Among these factors, epitaxial strain is particularly influential due to the strong polarization–strain coupling. The influence of strain and the reduced dimensionality on the energetics of the domain wall confined Bloch ferroelectric distortion was already emphasized in Ref. 33. In addition, some studies have demonstrated that the phase diagram of $\text{PbTiO}_3/\text{SrTiO}_3$ superlattices, under short-circuit electrical boundary conditions, evolves as a function of substrate lattice constant. The system transitions from a tetragonal phase under large compressive strain to polar skyrmion bubbles (with SrTiO_3 -imposed strain), then to vortex phases (with DyScO_3 -imposed strain), and finally to a_1/a_2 domain structures under large tensile strain.¹³ Even the coexistence of a_1/a_2 and vortex phases has been reported on DyScO_3 substrates,⁴⁵ while single-phase chiral vortex structures can be achieved by controlling epitaxial strain.⁴⁶

In this work, we explore the influence of mechanical boundary conditions on the stability of the Bloch component in 180° domain walls in bulk PbTiO_3 using the first-principles simulations.

II. METHODOLOGY

The simulations of 180° domains in bulk PbTiO_3 have been carried out with SIESTA within the generalized gradient approximation to the density functional theory, using the PBEsol functional.³⁶ Core electrons were replaced by *ab initio* norm-conserving fully separable pseudopotentials.⁴⁷ In this work, the optimized norm-conserving Vanderbilt pseudopotentials proposed by Hamann⁴⁸ were used, in the PSML format⁴⁹ available in the Pseudo-Dojo periodic table.^{50,51}

04 November 2025 18:21:29

The one-electron Kohn–Sham eigenstates were expanded in a basis of strictly localized⁵² numerical atomic orbitals.⁵³ Basis functions were obtained by finding the eigenfunctions of the isolated atoms confined within the soft-confinement spherical potential proposed in Ref. 54. A quadruple- ζ , double polarized basis set was used for the valence states of all the atoms. For the semicore states of Pb (5s, 5p, and 5d), and Ti (3s and 3p), a double- ζ quality was chosen. For Pb, an extra single- ζ 5f shell was included to increase angular flexibility. All the parameters that define the range and the shape of the atomic orbitals have been optimized variationally in bulk cubic centrosymmetric PbTiO₃ following the recipe given in Ref. 54.

The electronic density, Hartree, and exchange-correlation potentials, as well as the corresponding matrix elements between the basis orbitals, were calculated in a uniform real-space grid.⁵⁵ An equivalent plane wave cutoff of 1200 Ry was used to represent the charge density.

To assess the convergence of the numerical atomic orbital (NAO) basis set, we compared the results obtained with SIESTA against those from a highly converged plane wave calculation performed with ABINIT,^{56–58} using the same exchange-correlation functional and pseudopotentials. The plane wave results, with a very high energy cutoff (65 Ha), serve as a reference for the complete basis-set limit. Table I presents the lattice constants, atomic displacements, and spontaneous polarization of fully relaxed bulk tetragonal PbTiO₃ in its ferroelectric phase. Overall, we observe good agreement between the two codes and approaches. The tetragonality is slightly underestimated in SIESTA by approximately

TABLE I. Lattice constants (a and c) and atomic displacements of bulk PbTiO₃ in its ferroelectric tetragonal phase. The atomic displacements, measured relative to the centrosymmetric tetragonal positions, are expressed as a unit vector $\hat{\xi}$ multiplied by an amplitude $|\xi|$, following the approach in Ref. 35. ΔE represents the energy difference between the relaxed ferroelectric tetragonal structure and the centrosymmetric cubic phase. P_z^{BP} denotes the polarization magnitude along the z axis in the ferroelectric tetragonal unit cell computed from the Berry phase, while P_z^{BEC} is the polarization computed with the product of the Born effective charges computed at the cubic phase times the displacements of the atoms. Experimental data are sourced from Ref. 62.

	NAO	PW	Expt.
a (Å)	3.871	3.861	3.905
c (Å)	4.220	4.244	4.151
c/a	1.090	1.099	1.063
ξ_z (Pb)	0.696	0.699	0.718
ξ_z (Ti)	0.368	0.365	0.335
ξ_z (O _I)	−0.373	−0.363	−0.351
ξ_z (O _{II})	−0.373	−0.363	−0.351
ξ_z (O _{III})	−0.318	−0.338	−0.351
$\sum_i \xi_i$	0.000	0.000	0.000
$ \xi $ (Å)	0.490	0.510	0.434
ΔE (meV)	−79.38	−85.24	
P_z^{BEC} (C/m ²)	1.14	1.14	
P_z^{BP} (C/m ²)	0.96	0.99	

−0.8%. The largest discrepancy in atomic displacements occurs for the apical oxygen atom O_{III}, where the displacement along the z direction [$\xi_z(\text{O}_{\text{III}})$] is underestimated by −5.9%. The bulk spontaneous polarization can be computed as the change in polarization, along a continuous distortion path—from the centrosymmetric non-polar phase to the polar phase—using the Berry-phase approach.⁵⁹ This formal description as defined by the Berry-phase theory, yields a value of 0.96 C/m² with SIESTA, in comparison with 0.99 C/m² from ABINIT. Assuming constant Born effective charges along this path, the polarization change can alternatively be approximated by the sum of the product of the Born effective charges times the associated atomic displacements, divided by the unit cell volume.⁶⁰ Using Born effective charges calculated in the centrosymmetric cubic phase (resp. tetragonal phase), we obtain an effective polarization of 1.14 C/m² (resp. 0.84 C/m²) from both codes. The overestimation (resp. underestimation) relative to the Berry-phase polarization arises from the sensitivity of the Born charges to atomic displacements. More accurate estimates could be obtained by averaging the Born effective charges evaluated in both the high-symmetry and distorted structures. These differences will have implications for the layer-resolved polarization discussed in Sec. III A.

The five atom unit cell was replicated 20 times along the [100] direction, building a supercell consisting of $20 \times 1 \times 1$ perovskite unit cell (100 atoms in the simulation box), as shown in Fig. 1. Periodic boundary conditions along the three directions of space were applied in the supercell. This corresponds to performing the simulation under short-circuit electrostatic conditions. The domain wall is centered on a PbO plane, which is the energetically preferred configuration, as it exhibits a lower domain wall energy than the TiO₂-centered alternative.³⁵ Then, the bulk soft mode distortion shown in Table I was superimposed on the PbTiO₃ atoms, so the polarization points upward in half of the superlattice and downward in the other half. We take the domain wall to lie in the yz plane. With this choice of the coordinate system, the polarization within the interior of a domain points along the z direction, while the domain wall Bloch polarization lies along the y direction and the Néel component along the x direction. At this point, it is important to emphasize that the systems studied are bulk ferroelectrics (specifically PbTiO₃) without interfaces to dielectric or metallic layers that could give rise to bound surface charges. In addition, we are imposing periodic boundary conditions in all three spatial directions. This enforces continuity of the normal component of the polarization and precludes the formation of surface charges, thereby eliminating any macroscopic depolarization field along z . In the absence of significant depolarization fields, the true ground state of the system is monodomain. The domain structures analyzed in this work should, thus, be viewed as metastable configurations, stabilized under the considered specific conditions.

A $1 \times 8 \times 8$ k -point Monkhorst–Pack grid⁶¹ was used for integrations within the first Brillouin zone of the supercell and $8 \times 8 \times 8$ for the simulations of the monodomain phases with five atoms per unit cell.

In order to study the stability of the different domain configurations, we shall pay attention to three different magnitudes. The first is the energy cost required to form an Ising domain without

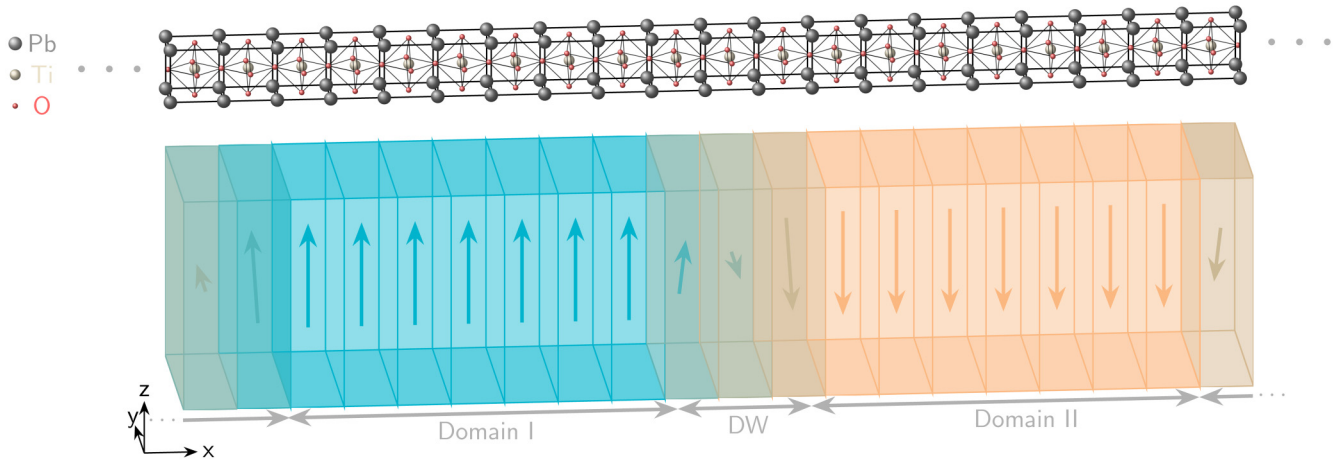


FIG. 1. Representation of the $20 \times 1 \times 1$ PbTiO_3 supercell featuring the domains and a domain wall with a Bloch-like component of the polarization using periodic boundary conditions.

any Néel or Bloch component with respect to the homogeneous ferroelectric phase. This will be referred to as the Ising domain wall energy, $E_{\text{DW}}^{\text{Ising}}$. It is computed from

$$E_{\text{DW}}^{\text{Ising}} = \frac{1}{2A} (E_{\text{sc}}^{\text{Ising}} - 20 \times E_{\text{bulk}}^{\text{ferro}}), \quad (1)$$

where $E_{\text{sc}}^{\text{Ising}}$ is the energy of the relaxed supercell where only the Ising domain is allowed to condense (i.e., atomic relaxation along z only), $E_{\text{bulk}}^{\text{ferro}}$ is the reference energy of the bulk structure (without domain walls), calculated from a single perovskite unit cell in the relaxed ferroelectric phase using a k -point mesh equivalent to the one used for the supercell. The factor of $1/2$ is due to the fact that in a supercell with periodic boundary conditions, there are two domain walls. A represents the area of the domain wall, computed from the corresponding lattice parameter within the supercell. Since the most stable structure in bulk PbTiO_3 under short-circuit boundary conditions is the monodomain ferroelectric phase, $E_{\text{DW}}^{\text{Ising}}$ is positive. Domain wall energies will be given in units of mJ/m^2 or in units of meV/\square , where \square represents the cell surface area of the domain wall.

The second relevant magnitude is the energy gain for condensing *only* the Néel component at the domain wall on top of the Ising configuration (i.e., atomic relaxation along z and x). This is referred to from now on as $E_{\text{DW}}^{\text{Néel}}$. It is computed by applying an equivalent relation as the one described by Eq. (1) with $E_{\text{sc}}^{\text{Ising}}$ replaced by $E_{\text{sc}}^{\text{Néel}}$, the energy of the relaxed structure allowing for a Néel component at the domain wall. During this process, the appearance of a Bloch component of the polarization at the domain wall is constrained. It is important to emphasize that the distinction we draw in this article between Ising and Néel-type domains is not commonly made in the literature. In many cases, the term “Ising domain” is used even when a Néel component and the associated inhomogeneous strain relaxations along the

x -direction are present. This is, for instance, the case of Refs. 33, 35, and 43. This practice arises because, upon structural relaxation, the Néel component develops naturally contrary to the Bloch component that requires an explicit breaking of symmetry to emerge.

Finally, if on top of the most stable Ising and Néel components of the polarization at the domain wall, we further allow the condensation of the Bloch component (i.e., atomic relaxation along x , y , and z), we can define $E_{\text{DW}}^{\text{Bloch}}$, again applying an equivalent relation as the one described by Eq. (1), but introducing $E_{\text{sc}}^{\text{Bloch}}$ as the energy of the most stable ferroelectric polarization (including both Néel and Bloch components). The difference between $E_{\text{DW}}^{\text{Bloch}}$ and $E_{\text{DW}}^{\text{Néel}}$ is particularly relevant to estimate the critical temperature upon which the Bloch component is unstable T_{C}^{DW} . Structural relaxations allowing for Bloch components were initialized from the previously relaxed Néel configuration, with Pb atoms at the domain wall displaced along the y -direction. The subsequent relaxations were performed using a conjugate-gradient method. Unless otherwise specified, all atomic relaxations were carried out using the SIESTA code, with convergence criteria of $0.01 \text{ eV}/\text{\AA}$ for the maximum component of the force on any atom and $0.0001 \text{ eV}/\text{\AA}^3$ for the maximum component of the stress tensor. For the atomic relaxation carried out using the ABINIT code, convergence criteria of $2.5 \times 10^{-3} \text{ eV}/\text{\AA}$ for the maximum component of the force on any atom and $2.5 \times 10^{-5} \text{ eV}/\text{\AA}^3$ for the maximum component of the stress tensor have been used.

III. RESULTS

A. Atomistic domain wall structures

The relaxed atomic structures of the supercell were obtained under various epitaxial strain conditions. These include (i) full relaxation of both atomic positions and lattice vectors; (ii) relaxation with lattice constants fixed to those of the optimized bulk tetragonal ferroelectric phase (see Table I); (iii) relaxation under

TABLE II. Calculated domain wall energies using the PBEsol functional under various epitaxial strain conditions for a supercell of $20 \times 1 \times 1$ u.c. (domain width of 10 u.c.). Lattice constants a , b , and c (in Å) correspond to the three Cartesian directions. P_0 (in C/m²) denotes the polarization at the center of the domain, and δ (in Å) is the half-width of the domain wall, both obtained by fitting the polarization profiles shown in Fig. 2 to the functional form given in Eq. (2). Domain wall energies are reported in both mJ/m² and meV/□ (in brackets).

a	b	c	P_0	δ	$E_{\text{DW}}^{\text{Ising}}$	$E_{\text{DW}}^{\text{Ising}} - E_{\text{DW}}^{\text{Néel}}$	$E_{\text{DW}}^{\text{Néel}} - E_{\text{DW}}^{\text{Bloch}}$
Fully relaxed configuration							
3.892	3.893	4.115	0.99	2.24	195.6 (195.4)	5.1 (5.1)	3.4 (3.3)
3.884	3.884	4.122	1.01	2.20	200.2 (200.1)	6.0 (6.2)	4.2 (4.2)
3.892 ⁴³	3.897 ⁴³	4.075 ⁴³			179.5 (178.0) ⁴³		6.4 (6.5) ⁴³
					152 (148.0) ³³		4.1 (4.0) ³³
PbTiO ₃ fixed to the optimized bulk tetragonal ferroelectric							
3.871	3.871	4.220	1.15	2.06	223.1 (227.5)	6.4 (6.6)	2.2 (2.2)
PbTiO ₃ strained on cubic SrTiO ₃							
3.889	3.889	4.120	0.99	2.21	195.6 (195.6)	5.0 (5.0)	3.0 (2.9)
PbTiO ₃ strained on cubic DyScO ₃							
3.912	3.912	4.071	0.92	2.39	224.9 (223.5)	5.0 (5.0)	10.2 (10.0)
PbTiO ₃ strained on orthorhombic DyScO ₃							
3.912	3.916	4.069	0.92	2.38	230.4 (229.0)	5.7 (5.6)	10.7 (10.6)
PbTiO ₃ strained on orthorhombic DyScO ₃							
3.916	3.912	4.065	0.91	2.45	229.4 (227.8)	5.0 (5.0)	9.8 (9.9)

the epitaxial constraint imposed by a hypothetical SrTiO₃ substrate; and (iv) relaxation under strain conditions corresponding to a DyScO₃ substrate, assuming either a square surface unit cell or an orthorhombic one with strains of -0.25% and -0.16% with respect to the theoretical bulk cubic lattice constant along the two in-plane directions.⁶³ The resulting lattice parameters for each case are summarized in Table II.

The corresponding layer-resolved polarization profiles are presented in Fig. 2. The local polarization is obtained within a linear approximation, using the same approach described in Sec. II for the computation of the spontaneous polarization^{33,35} in usual first-principles models of ferroelectrics.⁶⁴ The polarization is computed, as a product of the Born effective charges obtained for the bulk cubic centrosymmetric phase of PbTiO₃ times the displacement of the atoms with respect to a reference centrosymmetric phase on a five atom unit cell centered on Ti or Pb depending whether we are on a PbO or a TiO₂ plane.

Several conclusions can be drawn from the data in Fig. 2. First, the comparison between the results obtained using SIESTA and ABINIT for the fully relaxed structure [Fig. 2(a)] confirms excellent agreement for all three components of the polarization, validating the use of numerical atomic orbitals in domain wall calculations.

Second, consistent with prior findings,⁶⁵ the 180° ferroelectric domain walls are atomically narrow, with a width on the order of the lattice constant. The domain wall width was extracted by fitting the polarization profile to the functional form proposed by Gureev *et al.*,⁶⁶

$$P(x) = P_0 \tanh\left(\frac{x}{\delta}\right), \quad (2)$$

where δ denotes the characteristic half-width of the domain wall (i.e., to make the transition from $-P_0$ to P_0 , we need a space of around four times this length δ). The results, reported in Table II, reveal that δ increases with the in-plane lattice parameter, ranging from 2.06 Å at $a = 3.871$ –2.45 Å at $a = 3.916$ Å.

Third, the layer-by-layer polarization exhibits a plateau beginning at the second TiO₂ plane, with a saturation value of $P_0 = 0.99$ C/m² for the fully relaxed structure. This is somewhat lower than the bulk value of 1.14 C/m² reported in Table I, calculated using the same local polarization model. This discrepancy arises from the compromise that should be found between the c value at the domain and the c value at the domain wall. The c value obtained after relaxation of the full structure is $c = 4.115$ Å, i.e., 2.49% shorter than the relaxed value for the bulk tetragonal phase, and is dependent on the width of the domains. The reason for this shortening can be traced back to the strong polarization-strain coupling: the local c would naturally reduce near the domain wall where P_z vanishes and would tend to the bulk value at the center of the domain, where P_z saturates. Thus, a balance is found where the global c is reduced with respect to the bulk, with a concomitant increase in the in-plane lattice constant (a changes from 3.871 Å in the bulk ferroelectric tetragonal phase to 3.892 Å in the fully relaxed domain structure). Indeed, the local in-plane strain component, ϵ_1 in Voigt notation, computed with respect to the bulk tetragonal ferroelectric in-plane lattice constant, shows a uniform tensile strain of approximately 0.54% within the domain interior. This effect diminishes with increasing simulation box length along x , so the contribution to the total energy coming from the center of the domain increases with respect to the regions close to the domain wall.

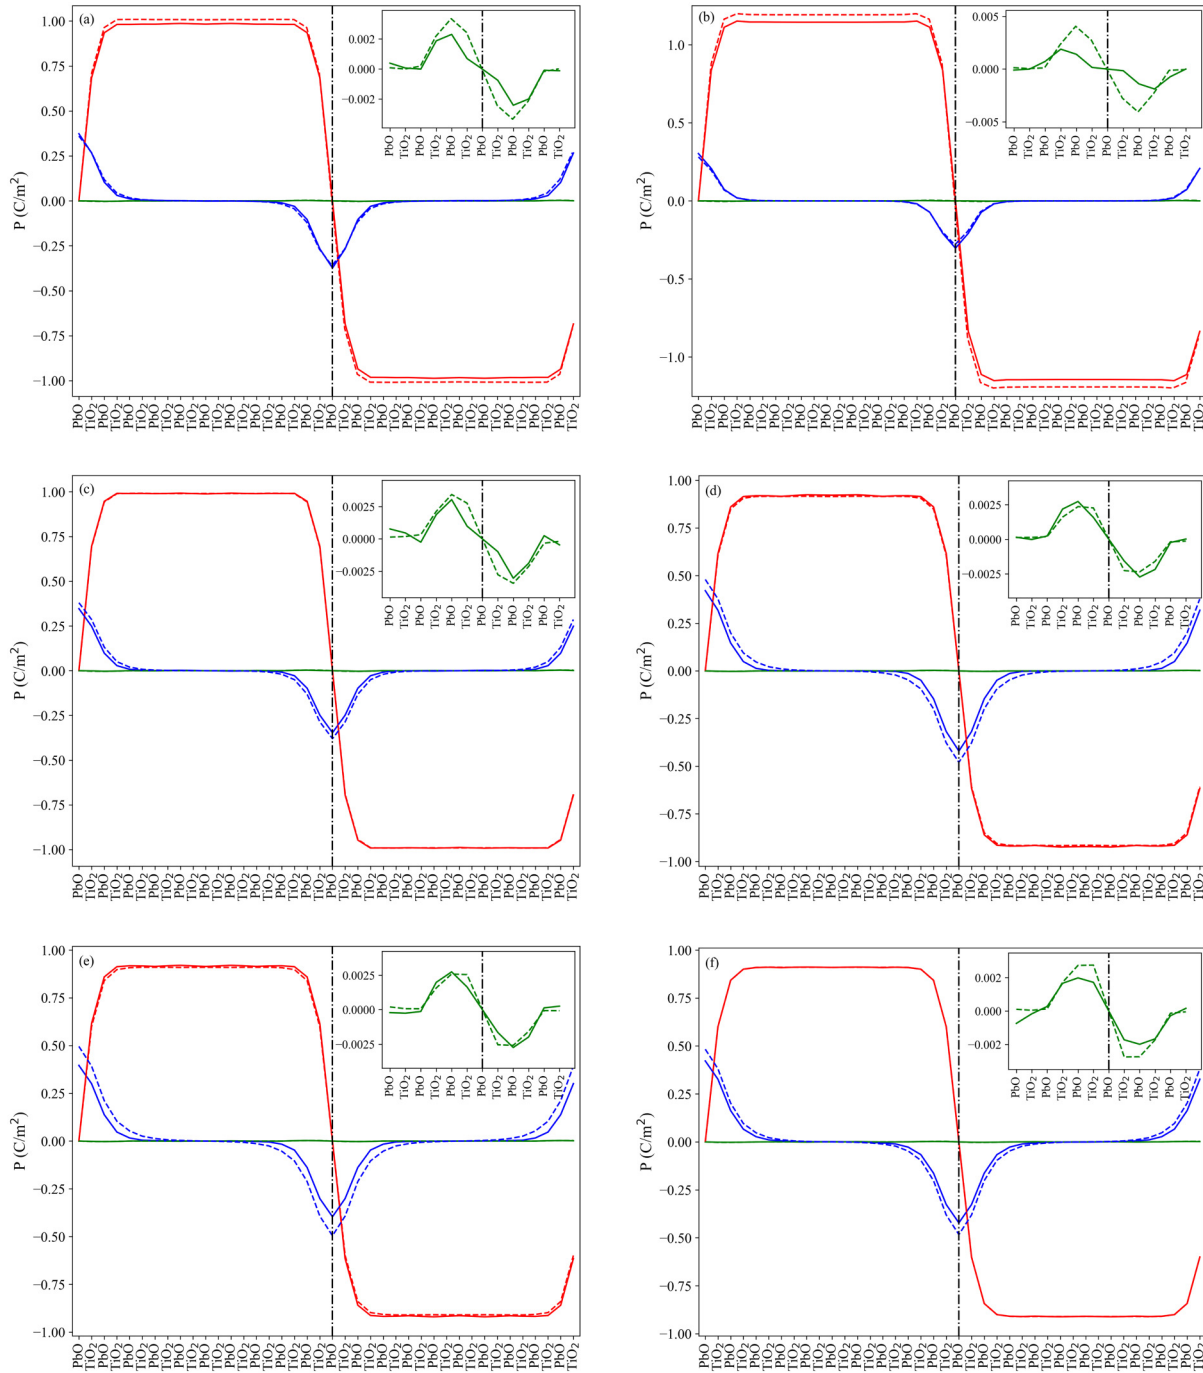


FIG. 2. Layer-resolved polarization profiles across 180° ferroelectric domains in bulk PbTiO_3 under six different epitaxial strain conditions: (a) full relaxation of atomic positions and lattice vectors; (b) relaxation with lattice parameters fixed to those of the optimized bulk tetragonal ferroelectric phase (see Table I); (c) relaxation under an epitaxial constraint mimicking a hypothetical SrTiO_3 substrate ($a = b = 3.889 \text{ \AA}$); (d) relaxation under strain corresponding to a DyScO_3 substrate with a square surface unit cell ($a = b = 3.912 \text{ \AA}$); (e) relaxation with orthorhombic DyScO_3 substrate constraints, $a = 3.912 \text{ \AA}$ and $b = 3.916 \text{ \AA}$; and (f) as in (e) but with $a = 3.916 \text{ \AA}$ and $b = 3.912 \text{ \AA}$. Components of the polarization along the three Cartesian directions are represented by green (P_x), blue (P_y), and red (P_z) lines. The full (dashed) lines correspond to the results obtained with SIESTA (ABINIT⁴⁶). Vertical dot-dashed lines mark the position of the PbO plane at the domain wall. Inset: zoom on the P_x component around the domain wall. Polarizations are given in C/m^2 .

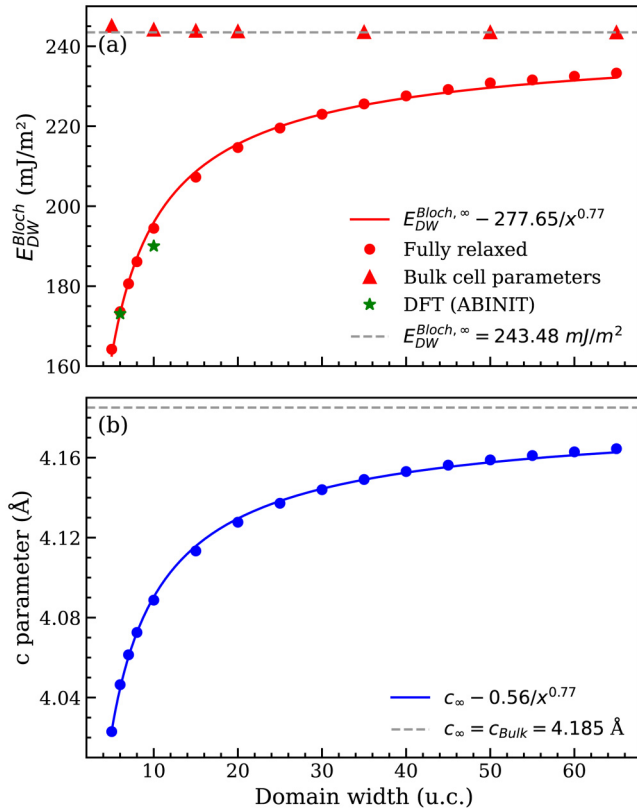


FIG. 5. (a) Convergence of the Bloch DW energies with respect to the domain width t in the fully relaxed case (red circles), constrained to the bulk tetragonal cell parameters case (red triangles) and ABINIT DFT fully relaxed results to which the model was fitted (green stars). The red curve represents a power-law fit to the energies on the fully relaxed case. (b) Convergence of the c lattice parameter with respect to the domain width (blue circles) fitted with a power-law (blue curve).

alters the domain wall density, which modifies the lattice parameters and, in turn, influences the DW energy, E_{DW} .

Alternatively, fixing the lattice parameters to their bulk values, as expected in the limit $t \rightarrow \infty$, provides a practical approach to estimate isolated DW energies from small supercells.³⁵ Figure 5 displays the evolution of c and E_{DW} as a function of t , obtained from second-principles simulations employing the model of Ref. 68. The results confirm that both quantities converge slowly when the lattice parameters are relaxed, exhibiting a power-law dependence on t . Consistent with previous findings,³⁵ we also show that fixing the lattice constants to their bulk values yields DW energies in excellent agreement with the extrapolated isolated DW limit, even for relatively small supercells. Unless otherwise stated, all DW energies reported in this work correspond to $t = 10$ unit cells and are, thus, specific to that domain width.

Given these considerations, we can now examine the results. Within the PBEsol functional, the energy differences associated with the domain wall in the fully relaxed configuration are

relatively large. For the high-symmetry case, where only the Ising-type configuration is allowed in the fully relaxed PbO-centered domain wall, these energies range from 152 (148 meV/\square), as reported in Ref. 33, to 195.6 mJ/m^2 (195.4 meV/\square) in our SIESTA calculations for fully relaxed lattice constants in a $20 \times 1 \times 1$ supercell. Meyer and Vanderbilt obtained a lower value of 132 mJ/m^2 (128.5 meV/\square) at the local density approximation (LDA) level using a $12 \times 1 \times 1$ and the lattice vectors constrained to the bulk tetragonal ferroelectric unit cell.³⁵ These significant discrepancies are unexpected, given the overall good agreement in the polarization profile and domain wall polarization. However, it is important to keep in mind that, as previously discussed, the “Ising” domain wall energies reported in Refs. 33, 35, and 43 correspond in reality to Néel wall energies following the notation of this article. While this is primarily a matter of nomenclature, it is nonetheless an important point to bear in mind when comparing energies. In addition, this variation can also be attributed to the differences in the DFT functional (LDA in Ref. 35 and PBEsol in Refs. 33 and 43 and in this work), pseudopotentials (projector augmented wave method in Ref. 33 vs optimized norm-conserving pseudopotentials used in this work and in Ref. 43), and basis sets (plane waves in Refs. 33 and 43 vs numerical atomic orbitals in this study). Notably, when the same pseudopotentials are used, the agreement in energy differences improves.

When a Néel-type polarization component is allowed at the domain wall, the energy decreases by approximately 5 mJ/m^2 (5.0 meV/\square), a value that is pretty constant independent of the strain conditions. This is surprising given that the Néel polarization at the domain wall is relatively small. As discussed in Sec. III A, this is attributed to the relaxation of the elastic energy produced by an inhomogeneous strain in the plane.

Furthermore, the full development of polarization at the domain wall, including a Bloch component, leads to an additional energy reduction that strongly depends on the imposed in-plane lattice constant. In the fully relaxed structure, this reduction (with respect to the most relaxed Néel structure) amounts to 3.4 mJ/m^2 (3.3 meV/\square), a value that remains nearly unchanged when PbTiO_3 is strained atop a cubic SrTiO_3 substrate (with a lattice parameter of 3.899 \AA , as computed using the PBEsol functional⁴³). However, under a tensile strain similar to that induced by a DyScO_3 substrate, the energy reduction due to the Bloch component nearly triples with respect to the value where only Néel polarization was allowed, increasing from 3.4 (3.3 meV/\square) to approximately 10.7 mJ/m^2 (10.6 meV/\square). This is somehow expected from previous studies on the phase diagram of bulk PbTiO_3 under strain. Tensile strains favor the polarization rotation from a purely tetragonal c -phase to a phase where the coexistence of c -domains and aa domains (with non-vanishing in-plane components) is favored.^{69,70} The fact that the P_x values are not increasing with strain arises from symmetry constraints that enforce head-to-head and tail-to-tail polarization configurations, which are energetically unfavorable due to electrostatics.

This increase in the well-depth also suggests that the critical transition temperature below which a Bloch-like domain wall stabilizes is highly strain-dependent. Second-principles simulations in Ref. 43 suggested that P_y became zero at approximately 150 K when PbTiO_3 was strained on cubic SrTiO_3 , while for freestanding PbTiO_3 (no imposed strain that resulted in slightly larger in-plane

lattice constants), a transition temperature equal to approximately 200 K was found. Further calculations with larger tensile strains should be performed for a proper numerical estimation of this temperature-strain dependence on the onset of the Bloch component.

IV. CONCLUSIONS

In this work, we have investigated the structural and energetic properties of Bloch-type polarization components in 180° domain walls in bulk PbTiO_3 under varying mechanical boundary conditions, using first-principles simulations. Our results provide a comprehensive atomistic understanding of how epitaxial strain influences the polarization profile and energetics of domain walls in this prototypical ferroelectric.

We confirm that a Bloch component, primarily originating from displacements of Pb atoms along the domain wall plane, can spontaneously develop at $T = 0$ K in otherwise Ising-type domain walls. The magnitude of this component, and the corresponding energy gain associated with its condensation, is found to be highly sensitive to the in-plane lattice constants. Specifically, tensile strains significantly enhance both the amplitude of the Bloch component and the associated energetic stabilization, with energy reductions reaching up to 10.7 mJ/m^2 ($10.6 \text{ meV}/\square$) under strain conditions mimicking DyScO_3 substrates.

Our analysis highlights the delicate interplay between structural relaxations, strain-induced elastic energy variations, and polarization orientation at domain walls. While the Ising component remains robust, the Bloch component arises in a relatively flat energy landscape. This behavior suggests that external control via mechanical boundary conditions could serve as a viable route to engineer chiral ferroelectric textures in bulk PbTiO_3 .

Finally, the strain dependence of the energy gain associated with the Bloch component provides a predictive framework to estimate the critical temperature for its stabilization, a critical magnitude to tailor topological and chiral functionalities in ferroelectric polar systems.

ACKNOWLEDGMENTS

S.C. acknowledges the financial support from Erasmus+ KA-107 action and the Vice-rectorate for the Internationalisation and Global Engagement of the University of Cantabria. J.J. acknowledges the financial support from Grant No. PID2022-139776NB-C63 funded by MCIN/AEI/10.13039/501100011033 and by ERDF “A way of making Europe” by the European Union. F.G.-O., L.B., and Ph.G. acknowledge the support by the European Union’s Horizon 2020 research and innovation program under Grant Agreement No. 964931 (TSAR). F.G.-O. also acknowledges the financial support from MSCA-PF 101148906 funded by the European Union and the Fonds de la Recherche Scientifique (FNRS) through the grant FNRS-CR 1.B.227.25F. Ph.G. also acknowledges the support from the Fonds de la Recherche Scientifique (FNRS) through the PDR project PROMOSPAN (Grant No. T.0107.20). The authors also acknowledge the computer resources, technical expertise, and assistance provided by the Centre for High Performance Computing (CHPC-MATS862), Cape Town, South Africa.

AUTHOR DECLARATIONS

Conflict of Interest

The authors have no conflicts to disclose.

Author Contributions

Stephen Chege: Conceptualization (equal); Data curation (equal); Formal analysis (equal); Investigation (equal); Writing – original draft (equal); Writing – review & editing (equal). **Louis Bastogne:** Data curation (equal); Formal analysis (equal); Investigation (equal); Writing – original draft (equal); Writing – review & editing (equal). **Fernando Gómez-Ortiz:** Conceptualization (equal); Data curation (equal); Formal analysis (equal); Investigation (equal); Writing – original draft (equal); Writing – review & editing (equal). **James Sifuna:** Supervision (equal). **George Amolo:** Funding acquisition (equal); Supervision (equal). **Philippe Ghosez:** Conceptualization (equal); Data curation (equal); Formal analysis (equal); Funding acquisition (equal); Investigation (equal); Writing – original draft (equal); Writing – review & editing (equal). **Javier Junquera:** Conceptualization (equal); Data curation (equal); Formal analysis (equal); Funding acquisition (equal); Investigation (equal); Methodology (equal); Project administration (equal); Resources (equal); Software (equal); Supervision (equal); Validation (equal); Visualization (equal); Writing – original draft (equal); Writing – review & editing (equal).

DATA AVAILABILITY

The data that support the findings of this study are available from the corresponding author upon reasonable request.

REFERENCES

- H. Fu and L. Bellaiche, “Ferroelectricity in barium titanate quantum dots and wires,” *Phys. Rev. Lett.* **91**, 257601 (2003).
- I. I. Naumov, L. Bellaiche, and H. Fu, “Unusual phase transitions in ferroelectric nanodisks and nanorods,” *Nature* **432**, 737 (2004).
- C.-L. Jia, K. W. Urban, M. Alexe, D. Hesse, and I. Vrejoiu, “Direct observation of continuous electric dipole rotation in flux-closure domains in ferroelectric $\text{Pb}(\text{Zr,Ti})\text{O}_3$,” *Science* **331**, 1420 (2011).
- Y. L. Tang, Y. L. Zhu, X. L. Ma, A. Y. Borisevich, A. N. Morozovska, E. A. Eliseev, W. Y. Wang, Y. J. Wang, Y. B. Xu, Z. D. Zhang, and S. J. Pennycook, “Observation of a periodic array of flux-closure quadrants in strained ferroelectric PbTiO_3 films,” *Science* **348**, 547 (2015).
- A. K. Yadav, C. T. Nelson, S. L. Hsu, Z. Hong, J. D. Clarkson, C. M. Schlepütz, A. R. Damodaran, P. Shafer, E. Arenholz, L. R. Dedon, D. Chen, A. Vishwanath, A. M. Minor, L. Q. Chen, J. F. Scott, L. W. Martin, and R. Ramesh, “Observation of polar vortices in oxide superlattices,” *Nature* **530**, 198 (2016).
- Y. Nahas, S. Prokhorenko, L. Louis, Z. Gui, I. Kornev, and L. Bellaiche, “Discovery of stable skyrmionic state in ferroelectric nanocomposites,” *Nat. Commun.* **6**, 8542 (2015).
- M. A. Pereira Gonçalves, C. Escorihuela-Sayalero, P. Garca-Fernández, J. Junquera, and J. Íñiguez, “Theoretical guidelines to create and tune electric skyrmion bubbles,” *Sci. Adv.* **5**, eaau7023 (2019).
- S. Das, Y. L. Tang, Z. Hong, M. A. P. Gonçalves, M. R. McCarter, C. Klewe, K. X. Nguyen, F. Gómez-Ortiz, P. Shafer, E. Arenholz, V. A. Stoica, S.-L. Hsu, B. Wang, C. Ophus, J. F. Liu, C. T. Nelson, S. Saremi, B. Prasad, A. B. Mei, D. G. Schlom, J. Íñiguez, P. García-Fernández, D. A. Muller, L. Q. Chen, J. Junquera, L. W. Martin, and R. Ramesh, “Observation of room-temperature polar skyrmions,” *Nature* **568**, 368 (2019).

- ⁹Y. Nahas, S. Prokhorenko, Q. Zhang, V. Govinden, N. Valanoor, and L. Bellaiche, "Topology and control of self-assembled domain patterns in low-dimensional ferroelectrics," *Nat. Commun.* **11**, 5779 (2020).
- ¹⁰Y. J. Wang, Y. P. Feng, Y. L. Zhu, Y. L. Tang, L. X. Yang, M. J. Zou, W. R. Geng, M. J. Han, X. W. Guo, B. Wu, and X. L. Ma, "Polar meron lattice in strained oxide ferroelectrics," *Nat. Mater.* **19**, 881 (2020).
- ¹¹Y.-T. Shao, S. Das, Z. Hong, R. Xu, S. Chandrika, F. Gómez-Ortiz, P. García-Fernández, L.-Q. Chen, H. Y. Hwang, J. Junquera, L. W. Martin, R. Ramesh, and D. A. Muller, "Emergent chirality in a polar meron to skyrmion phase transition," *Nat. Commun.* **14**, 1355 (2023).
- ¹²I. Luk'yanchuk, Y. Tikhonov, A. Razumnaya, and V. M. Vinokur, "Hopfions emerge in ferroelectrics," *Nat. Commun.* **11**, 2433 (2020).
- ¹³J. Junquera, Y. Nahas, S. Prokhorenko, L. Bellaiche, J. Íñiguez, D. G. Schlom, L.-Q. Chen, S. Salahuddin, D. A. Muller, L. W. Martin, and R. Ramesh, "Topological phases in polar oxide nanostructures," *Rev. Mod. Phys.* **95**, 025001 (2023).
- ¹⁴V. Govinden, S. Prokhorenko, Q. Zhang, S. Rijal, Y. Nahas, L. Bellaiche, and N. Valanoor, "Spherical ferroelectric solitons," *Nat. Mater.* **22**, 553 (2023).
- ¹⁵Y. Wang, Y. Tang, Y. Zhu, and X. Ma, "Entangled polarizations in ferroelectrics: A focused review of polar topologies," *Acta Mater.* **243**, 118485 (2023).
- ¹⁶P. Zubko, J. C. Wojdel, M. Hadjimichael, S. Fernandez-Pena, A. Sené, I. Luk'yanchuk, J.-M. Triscone, and J. Íñiguez, "Negative capacitance in multidomain ferroelectric superlattices," *Nature* **534**, 524 (2016).
- ¹⁷A. K. Yadav, K. X. Nguyen, Z. Hong, P. García-Fernández, P. Aguado-Puente, C. T. Nelson, S. Das, B. Prasad, D. Kwon, S. Cheema, A. I. Khan, C. Hu, J. Íñiguez, J. Junquera, L.-Q. Chen, D. A. Muller, R. Ramesh, and S. Salahuddin, "Spatially resolved steady-state negative capacitance," *Nature* **565**, 468 (2019).
- ¹⁸J. Íñiguez, P. Zubko, I. Luk'yanchuk, and A. Cano, "Ferroelectric negative capacitance," *Nat. Rev. Mater.* **4**, 243 (2019).
- ¹⁹P. Shafer, P. García-Fernández, P. Aguado-Puente, A. R. Damodaran, A. K. Yadav, C. T. Nelson, S.-L. Hsu, J. C. Wojdel, J. Íñiguez, L. W. Martin, E. Arenholz, J. Junquera, and R. Ramesh, "Emergent chirality in the electric polarization texture of titanate superlattices," *Proc. Natl. Acad. Sci. U.S.A.* **115**, 915 (2018).
- ²⁰S. W. Lovesey and G. van der Laan, "Resonant x-ray diffraction from chiral electric-polarization structures," *Phys. Rev. B* **98**, 155410 (2018).
- ²¹K. T. Kim, M. R. McCarter, V. A. Stoica, S. Das, C. Klewe, E. P. Donoway, D. M. Burn, P. Shafer, F. Rodolakis, M. A. P. Gonçalves, F. Gómez-Ortiz, J. Íñiguez, P. García-Fernández, J. Junquera, S. Susarla, S. W. Lovesey, G. van der Laan, S. Y. Park, L. W. Martin, J. W. Freeland, R. Ramesh, and D. R. Lee, "Chiral structures of electric polarization vectors quantified by x-ray resonant scattering," *Nat. Commun.* **13**, 1769 (2022).
- ²²M. R. McCarter, K. T. Kim, V. A. Stoica, S. Das, C. Klewe, E. P. Donoway, D. M. Burn, P. Shafer, F. Rodolakis, M. A. P. Gonçalves, F. Gómez-Ortiz, J. Íñiguez, P. García-Fernández, J. Junquera, S. W. Lovesey, G. van der Laan, S. Y. Park, J. W. Freeland, L. W. Martin, D. R. Lee, and R. Ramesh, "Structural chirality of polar skyrmions probed by resonant elastic x-ray scattering," *Phys. Rev. Lett.* **129**, 247601 (2022).
- ²³I. Luk'yanchuk, A. Razumnaya, S. Kondovych, Y. Tikhonov, and V. M. Vinokur, "Topological ferroelectric chirality," *arXiv:2406.19728 [cond-mat.mtrl-sci]* (2024).
- ²⁴I. A. Lukyanchuk, A. G. Razumnaya, S. Kondovych, Y. A. Tikhonov, B. Khesin, and V. M. Vinokur, "Topological foundations of ferroelectricity," *Phys. Rep.* **1110**, 1 (2025).
- ²⁵G. H. Fecher, J. Kübler, and C. Felser, "Chirality in the solid state: Chiral crystal structures in chiral and achiral space groups," *Materials* **15**, 5812 (2022).
- ²⁶E. Bousquet, M. Fava, Z. Romestan, F. Gómez-Ortiz, E. E. McCabe, and A. H. Romero, "Structural chirality and related properties in periodic inorganic solids: Review and perspectives," *J. Phys.: Condens. Matter* **37**, 163004 (2025).
- ²⁷I. Dzyaloshinsky, "A thermodynamic theory of "weak" ferromagnetism of antiferromagnetics," *J. Phys. Chem. Solids* **4**, 241 (1958).
- ²⁸T. Moriya, "Anisotropic superexchange interaction and weak ferromagnetism," *Phys. Rev.* **120**, 91 (1960).
- ²⁹K. C. Erb and J. Hlinka, "Vector, bidirector, and Bloch skyrmion phases induced by structural crystallographic symmetry breaking," *Phys. Rev. B* **102**, 024110 (2020).
- ³⁰H. J. Zhao, P. Chen, S. Prosandeev, S. Artyukhin, and L. Bellaiche, "Dzyaloshinskii-Moriya-like interaction in ferroelectrics and antiferroelectrics," *Nat. Mater.* **20**, 341 (2021).
- ³¹P. Chen, H. J. Zhao, S. Prosandeev, S. Artyukhin, and L. Bellaiche, "Microscopic origin of the electric Dzyaloshinskii-Moriya interaction," *Phys. Rev. B* **106**, 224101 (2022).
- ³²L. Louis, I. Kornev, G. Geneste, B. Dkhil, and L. Bellaiche, "Novel complex phenomena in ferroelectric nanocomposites," *J. Phys.: Condens. Matter* **24**, 402201 (2012).
- ³³J. C. Wojdel and J. Íñiguez, "Ferroelectric transitions at ferroelectric domain walls found from first principles," *Phys. Rev. Lett.* **112**, 247603 (2014).
- ³⁴D. Lee, R. K. Behera, P. Wu, H. Xu, Y. L. Li, S. B. Sinnott, S. R. Phillpot, L. Q. Chen, and V. Gopalan, "Mixed Bloch-Néel-Ising character of 180° ferroelectric domain walls," *Phys. Rev. B* **80**, 060102 (2009).
- ³⁵B. Meyer and D. Vanderbilt, "Ab initio study of ferroelectric domain walls in PbTiO₃," *Phys. Rev. B* **65**, 104111 (2002).
- ³⁶J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou, and K. Burke, "Restoring the density-gradient expansion for exchange in solids and surfaces," *Phys. Rev. Lett.* **100**, 136406 (2008).
- ³⁷Y. J. Wang, D. Chen, Y. L. Tang, Y. L. Zhu, and X. L. Ma, "Origin of the Bloch-type polarization components at the 180° domain walls in ferroelectric PbTiO₃," *J. Appl. Phys.* **116**, 224105 (2014).
- ³⁸Y.-J. Wang, Y.-L. Zhu, and X.-L. Ma, "Chiral phase transition at 180° domain walls in ferroelectric PbTiO₃ driven by epitaxial compressive strains," *J. Appl. Phys.* **122**, 134104 (2017).
- ³⁹P. Behera, M. A. May, F. Gómez-Ortiz, S. Susarla, S. Das, C. T. Nelson, L. Caretta, S.-L. Hsu, M. R. McCarter, B. H. Savitzky, E. S. Barnard, A. Raja, Z. Hong, P. García-Fernández, S. W. Lovesey, G. van der Laan, P. Erccius, C. Ophus, L. W. Martin, J. Junquera, M. B. Raschke, and R. Ramesh, "Electric field control of chirality," *Sci. Adv.* **8**, eabj8030 (2022).
- ⁴⁰P. Aguado-Puente and J. Junquera, "Structural and energetic properties of domains in PbTiO₃/SrTiO₃ superlattices from first principles," *Phys. Rev. B* **85**, 184105 (2012).
- ⁴¹J. Yang and S. Liu, "Topological phase transitions in perovskite superlattices driven by temperature, electric field, and doping," *Phys. Rev. B* **110**, 214112 (2024).
- ⁴²S. Zheng, J. Zhang, A. Li, and J. Wang, "Origin of chiral phase transition of polar vortex in ferroelectric/dielectric superlattices," *Nano Lett.* **25**, 1397 (2025).
- ⁴³E. Zatterin, P. Ondrejovic, L. Bastogne, C. Lichtensteiger, L. Tovaglieri, D. A. Chaney, A. Sasani, T. Schüll, A. Bosak, S. Leake, P. Zubko, P. Ghosez, J. Hlinka, J.-M. Triscone, and M. Hadjimichael, "Assessing the ubiquity of Bloch domain walls in ferroelectric lead titanate superlattices," *Phys. Rev. X* **14**, 041052 (2024).
- ⁴⁴C. Weymann, S. Cherifi-Hertel, C. Lichtensteiger, I. Gaponenko, K. D. Dorkenoo, A. B. Naden, and P. Paruch, "Non-Ising domain walls in c-phase ferroelectric lead titanate thin films," *Phys. Rev. B* **106**, L241404 (2022).
- ⁴⁵A. R. Damodaran, J. D. Clarkson, Z. Hong, H. Liu, A. K. Yadav, C. T. Nelson, S.-L. Hsu, M. R. McCarter, K.-D. Park, V. Kravtsov, A. Farhan, Y. Dong, Z. Cai, H. Zhou, P. Aguado-Puente, P. García-Fernández, J. Íñiguez, J. Junquera, A. Scholl, M. B. Raschke, L.-Q. Chen, D. D. Fong, R. Ramesh, and L. W. Martin, "Phase coexistence and electric-field control of toroidal order in oxide superlattices," *Nat. Mater.* **16**, 1003 (2017).
- ⁴⁶S. Das, M. R. McCarter, F. Gómez-Ortiz, Y.-L. Tang, Z. Hong, A. Ghosh, P. Shafer, P. García-Fernández, J. Junquera, L. W. Martin, and R. Ramesh, "Pure chiral polar vortex phase in PbTiO₃/SrTiO₃ superlattices with tunable circular dichroism," *Nano Lett.* **23**, 6602 (2023).
- ⁴⁷L. Kleinman and D. M. Bylander, "Efficacious form for model pseudopotentials," *Phys. Rev. Lett.* **48**, 1425 (1982).
- ⁴⁸D. Hamann, "Optimized norm-conserving Vanderbilt pseudopotentials," *Phys. Rev. B* **88**, 085117 (2013).

- ⁴⁹A. García, M. J. Verstraete, Y. Pouillon, and J. Junquera, "The PSML format and library for norm-conserving pseudopotential data curation and interoperability," *Comput. Phys. Commun.* **227**, 51 (2018).
- ⁵⁰M. Van Setten, M. Giantomassi, E. Bousquet, M. J. Verstraete, D. R. Hamann, X. Gonze, and G.-M. Rignanese, "The PSEUDOJOJO: Training and grading a 85 element optimized norm-conserving pseudopotential table," *Comput. Phys. Commun.* **226**, 39 (2018).
- ⁵¹The scalar relativistic ONCVSP v0.4.1 pseudopotentials with stringent accuracy were used.
- ⁵²O. F. Sankey and D. J. Niklewski, "Ab initio multicenter tight-binding model for molecular-dynamics simulations and other applications in covalent systems," *Phys. Rev. B* **40**, 3979 (1989).
- ⁵³E. Artacho, D. Sánchez-Portal, P. Ordejón, A. García, and J. M. Soler, "Linear-scaling ab-initio calculations for large and complex systems," *Phys. Status Solidi B* **215**, 809 (1999).
- ⁵⁴J. Junquera, O. Paz, D. Sánchez-Portal, and E. Artacho, "Numerical atomic orbitals for linear-scaling calculations," *Phys. Rev. B* **64**, 235111 (2001).
- ⁵⁵J. M. Soler, E. Artacho, J. D. Gale, A. García, J. Junquera, P. Ordejón, and D. Sánchez-Portal, "The SIESTA method for ab initio order-N materials simulation," *J. Phys.: Condens. Matter* **14**, 2745 (2002).
- ⁵⁶X. Gonze, B. Amadon, P.-M. Anglade, J.-M. Beuken, F. Bottin, P. Boulanger, F. Bruneval, D. Caliste, R. Caracas, M. Côté, T. Deutsch, L. Genovese, P. Ghosez, M. Giantomassi, S. Goedecker, D. Hamann, P. Hermet, F. Jollet, G. Jomard, S. Leroux, M. Mancini, S. Mazevet, M. Oliveira, G. Onida, Y. Pouillon, T. Rangel, G.-M. Rignanese, D. Sangalli, R. Shaltaf, M. Torrent, M. Verstraete, G. Zerah, and J. Zwanziger, "ABINIT: First-principles approach to material and nanosystem properties," *Comput. Phys. Commun.* **180**, 2582 (2009).
- ⁵⁷X. Gonze, F. Jollet, F. Abreu Araujo, D. Adams, B. Amadon, T. Applencourt, C. Audouze, J.-M. Beuken, J. Bieder, A. Bokhanchuk, E. Bousquet, F. Bruneval, D. Caliste, M. Côté, F. Dahm, F. Da Pieve, M. Delaveau, M. Di Gennaro, B. Dorado, C. Espejo, G. Geneste, L. Genovese, A. Gerossier, M. Giantomassi, Y. Gillet, D. Hamann, L. He, G. Jomard, J. Laflamme Janssen, S. Le Roux, A. Levitt, A. Lherbier, F. Liu, I. Lukačević, A. Martin, C. Martins, M. Oliveira, S. Poncé, Y. Pouillon, T. Rangel, G.-M. Rignanese, A. Romero, B. Rousseau, O. Rubel, A. Shukri, M. Stankovski, M. Torrent, M. Van Setten, B. Van Troeye, M. Verstraete, D. Waroquiers, J. Wiktor, B. Xu, A. Zhou, and J. Zwanziger, "Recent developments in the ABINIT software package," *Comput. Phys. Commun.* **205**, 106 (2016).
- ⁵⁸X. Gonze, B. Amadon, G. Antonius, F. Arnardi, L. Baguet, J.-M. Beuken, J. Bieder, F. Bottin, J. Bouchet, E. Bousquet, N. Brouwer, F. Bruneval, G. Brunin, T. Cavnac, J.-B. Charraud, W. Chen, M. Côté, S. Cottenier, J. Denier, G. Geneste, P. Ghosez, M. Giantomassi, Y. Gillet, O. Gingras, D. R. Hamann, G. Hautier, X. He, N. Helbig, N. Holzwarth, Y. Jia, F. Jollet, W. Lafargue-Dit-Hauret, K. Lejaeghere, M. A. Marques, A. Martin, C. Martins, H. P. Miranda, F. Naccarato, K. Persson, G. Petretto, V. Planes, Y. Pouillon, S. Prokhorenko, F. Ricci, G.-M. Rignanese, A. H. Romero, M. M. Schmitt, M. Torrent, M. J. van Setten, B. Van Troeye, M. J. Verstraete, G. Zerah, and J. W. Zwanziger, "The ABINIT project: Impact, environment and recent developments," *Comput. Phys. Commun.* **248**, 107042 (2020).
- ⁵⁹D. Vanderbilt, *Berry Phases in Electronic Structure Theory. Electric Polarization, Orbital Magnetization and Topological Insulators* (Cambridge University Press, Cambridge, 2018).
- ⁶⁰P. Ghosez, J.-P. Michenaud, and X. Gonze, "Dynamical atomic charges: The case of ABO₃ compounds," *Phys. Rev. B* **58**, 6224 (1998).
- ⁶¹H. J. Monkhorst and J. D. Pack, "Special points for Brillouin-zone integrations," *Phys. Rev. B* **13**, 5188 (1976).
- ⁶²F. Jona and G. Shirane, *Ferroelectric Crystals*, Dover Books on Engineering (Dover Publications, 1993).
- ⁶³L. Tovaglieri, M. Hadjimichael, P. Torruella, C.-Y. Hsu, L. Korosec, D. T. L. Alexander, P. Paruch, J.-M. Triscone, and C. Lichtensteiger, "Investigating domain structures and superdomains in ferroelectric PbTiO₃ based heterostructures on DyScO₃," *APL Mater.* **13**, 021118 (2025).
- ⁶⁴W. Zhong, D. Vanderbilt, and K. M. Rabe, "First-principles theory of ferroelectric phase transitions for perovskites: The case of BaTiO₃," *Phys. Rev. B* **52**, 6301 (1995).
- ⁶⁵G. Catalan, J. Seidel, R. Ramesh, and J. F. Scott, "Domain wall nanoelectronics," *Rev. Mod. Phys.* **84**, 119 (2012).
- ⁶⁶M. Y. Gureev, A. K. Tagantsev, and N. Setter, "Head-to-head and tail-to-tail 180° domain walls in an isolated ferroelectric," *Phys. Rev. B* **83**, 184104 (2011).
- ⁶⁷S. Pöykkö and D. J. Chadi, "Ab initio study of 180° domain wall energy and structure in PbTiO₃," *Appl. Phys. Lett.* **75**, 2830 (1999).
- ⁶⁸L. Bastogne and P. Ghosez, "Ferroelectric properties and topological textures in PbTiO₃ from a second-principles open-source interatomic potential," *arXiv:2505.02624* [cond-mat.mtrl-sci] (2025).
- ⁶⁹C. Bungaro and K. M. Rabe, "Epitaxially strained (PbTiO₃)₁/(PbZrO₃)₁ superlattice and PbTiO₃ from first principles," *Phys. Rev. B* **69**, 184101 (2004).
- ⁷⁰O. Diéguez, K. M. Rabe, and D. Vanderbilt, "First-principles study of epitaxial strain in perovskites," *Phys. Rev. B* **72**, 144101 (2005).